Middle-East Journal of Scientific Research 21 (3): 477-486, 2014
ISSN 1990-9233
© IDOSI Publications, 2014
DOI: 10.5829/idosi.mejsr.2014.21.03.21161

Frictional Behavior of Polymers Sliding Against Smooth and Rough Mild Steel Counter Faces

[1]*Mohammad Asaduzzaman Chowdhury,* [2]*Dewan Muhammad Nuruzzaman,*
[1]*Arefin Kowser,* [1]*Mostafizur Rahman,* [1]*Biplov Kumar Roy,* [1]*Soma Chakraborty,*
[1]*Sagir Hossen,* [1]*Imam Uddin and* [1]*Selim Hossain*

[1]Dhaka University of Engineering and Technology, Gazipur, Gazipur-1700, Bangladesh
[2]Faculty of Manufacturing Engineering, University Malaysia Pahang, Malaysia

Abstract: In the present study, friction coefficient and wear rate of polytetrafluoroethylene (commercially known as teflon) and nylon sliding against mild steel are investigated experimentally. In order to do so, a pin on disc apparatus is designed and fabricated. Experiments are carried out when smooth or rough mild steel pin slides on teflon and nylon disc. Experiments are conducted at normal load 10, 15 and 20 N, sliding velocity 1, 1.5 and 2 m/s and relative humidity 70%. Variations of friction coefficient with the duration of rubbing at different normal loads and sliding velocities are investigated. Results show that friction coefficient is influenced by duration of rubbing, normal load and sliding velocity. In general, friction coefficient increases for a certain duration of rubbing and after that it remains constant for the rest of the experimental time. The obtained results reveal that friction coefficient decreases with the increase in normal load for teflon and nylon mating with smooth or rough mild steel counter face. On the other hand, it is also found that friction coefficient increases with the increase in sliding velocity for both of the tested materials. Moreover, wear rate increases with the increase in normal load and sliding velocity. The magnitudes of friction coefficient and wear rate are different depending on sliding velocity and normal load for both smooth and rough counterface pin materials.

Key words: Friction coefficient · Wear rate · Teflon · Nylon · Mild steel · Normal load · Sliding velocity

INTRODUCTION

Numerous investigations have been carried out on friction and wear of different materials under different operating conditions. Several researchers [1-6] observed that the friction force and wear rate depend on roughness of the rubbing surfaces, relative motion, type of material, temperature, normal force, relative humidity, vibration, etc. The parameters that dictate the tribological performance of polymer and its composites include polymer molecular structure, processing and treatment, properties, viscoelastic behavior, surface texture, etc. [7-10]. There have been also a number of investigations exploring the influence of test conditions, contact geometry and environment on the friction and wear behavior of polymers and composites. [11-13] reported that the tribological behavior of polyamide, high density polyethylene and their composites is greatly affected by normal load, sliding speed and temperature. [14-15] showed that applied load and sliding speed play significant role on the wear behavior of polymer and composites. They also showed that applied load has more effect on the wear than the speed for composites. Experiments were carried out on friction and wear behavior of poly-ether-imide and its composites under different operating conditions [16-19]. Polymers and its composites are extensively used in sliding/rolling components such as gears, cams, bearings, rollers, transmission belts and grinding mills where their self lubricating properties are exploited to avoid the need for oil or grease lubrication with its attendant problems of contamination [20, 21]. However, when the contact between sliding pairs is present, there is the problem of friction and wear. [22-24] demonstrated that the friction

Corresponding Author: Mohammad Asaduzzaman Chowdhury, Dhaka University of Engineering and Technology, Gazipur, Gazipur-1700, Bangladesh.

coefficient can, generally, be reduced and the wear resistance increased by selecting the right material combinations.

It was reported [25-27] that the influence of sliding speed on friction and wear of polymer and its composite is greater than that of applied load though some other researchers have different views. Unal *et al*. [28, 29] reported that the applied load exerts greater influence on the sliding wear of polymer and its composites than the sliding speed. Transfer film has important effects on the tribological behavior of polymer and its' composite. If the transfer film is thin, uniform and continuous, the wear loss and the friction coefficient are low [30]. The results by [31, 32] showed that tribological performance of polymer material can be improved significantly by fibre reinforcement or fillers. The reason was that the transfer films formed and adhered close on the surface of counterface material during friction which resulted in the increase in wear resistance of the composites [31, 10]. It was showed [33] that reinforcement of fibre or filler significantly improves the tribological behavior of polymeric material but this is not necessarily true for all cases. Franklin [34] reported that wear behavior of polymers under dry reciprocating sliding conditions does not always follow the generally accepted engineering rule of 'higher sliding speed, the higher wear rate'. The influence of normal load on the friction coefficient and wear rate of different polymer and composite materials was investigated [35] and it was found that the values of friction coefficient and wear rate are different for different materials. Several researchers [36-39] reported that friction coefficient of polymers and its composites rubbing against metal increases or decreases depending on the range of sliding speed and sliding pairs. Researchers [40-43] have also observed that the friction coefficient of polymers and its composites rubbing against metals decreases with the increase in load though some other researchers have different views. It was showed [45-47] that value of friction coefficient increases with the increase in load. Friction coefficient and specific wear rate values for different combinations of polymer and its composite were obtained and compared [27]. For all material combinations, it was observed that the coefficient of friction decreases linearly with the increase in applied pressure values. Unal *et al*. [37, 29] reported that the applied load exerts greater influence on the sliding wear of polymer and its composite than the sliding velocity. Friction and wear behavior of glass fiber-reinforced polyester composite were studied and results showed that in general, friction and wear are strongly influenced by all the test parameters such as applied load, sliding speed, sliding distance and fiber orientations [48]. Moreover, it was found that applied normal load, sliding speed and fiber orientations have more pronounced effect on wear rate than sliding distance. Wang and Li [26] observed that the sliding velocity has more significant effect on the sliding wear as compared to the applied load and variations of wear rate with operating time can be distinguished by three distinct periods. These periods are running-in period, steady state period and severe wear period, respectively. The friction and the wear behavior of the polymeric material depend on the nature, thickness and stability of the transfer film that is formed and on the properties of the metallic counter face material [49]. Yang [50] studied the transfer of polytetrafluoroethylene (PTFE) on to 316 stainless steel and silicon wafers using infrared spectrophotometry and founds that it was strongly time and temperature dependent and reached a steady state after a certain period of contact. Tsukizoe and Ohmae [33] showed that reinforcement of fiber or filler significantly improve the tribological behavior of polymeric material but this is not necessarily true for all cases. Suresha *et al*. [38] showed that there is a strong inter-dependence on the friction coefficient and wear loss with respect to the applied loads for steel composites contact. It was found that the coefficient of friction and wear loss increase with the increase in applied normal load for all the samples evaluated.

From the aforementioned research works, it can be concluded that friction coefficient of polymer materials at different normal loads and sliding velocities differs significantly. Even now a day, the effect of normal load and sliding velocity on friction coefficient and wear rate of polymer materials such as teflon and nylon sliding against different counterface surface conditions is less understood. This means that more research work is needed for a better understanding of friction coefficient and wear rate of these materials under different normal loads and sliding velocities for smooth and rough mild steel counterfaces. Therefore, in order to understand more clearly, in this study experiments are carried out to investigate the influence of normal loads and sliding velocities on friction coefficient and wear rate of teflon and nylon. The effects of duration of rubbing on friction coefficient of these materials are also examined in this study.

Experimental: A schematic diagram of the experimental set-up is shown in Fig. 1 i.e. a pin which can slide on a rotating horizontal surface (disc). In this set-up a circular test sample (disc) is to be fixed on a rotating plate (table) having a long vertical shaft clamped with screw from the

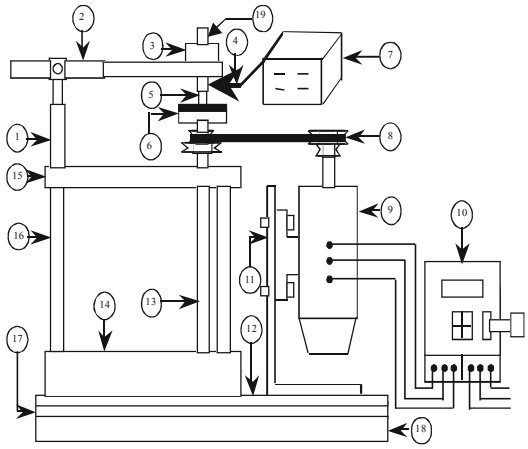

Fig. 1: Block diagram of the experimental set-up

Table 1: Experimental Conditions

Sl. No.	Parameters	Operating Conditions
1.	Normal Load	10, 15, 20 N
2.	Sliding Velocity	1, 1.5, 2 m/s
3.	Relative Humidity	70 (± 5)%
4.	Duration of Rubbing	30 minutes
5.	Surface Condition	Dry
6.	Disc material	(I) Polytetrafluoroethylene (Teflon) (ii) Nylon
7.	Roughness of Teflon and Nylon, R_a	0.55-0.65 µm
8.	Pin material	Mild steel
9.	Roughness of mild steel, R_a	(a) Smooth counterface: about 0.30 µm (b) Rough counterface: about 3.0 µm

bottom surface of the rotating plate. The shaft passes through two close-fit bush-bearings which are rigidly fixed with stainless steel plate and stainless steel base such that the shaft can move only axially and any radial movement of the rotating shaft is restrained by the bush. These stainless steel plate and stainless steel base are rigidly fixed with four vertical round bars to provide the rigidity to the main structure of this set-up. The main base of the set-up is constructed by 10 mm thick mild steel plate consisting of 3 mm thick rubber sheet at the upper side and 20 mm thick rubber block at the lower side. A compound V-pulley above the top stainless steel plate was fixed with the shaft to transmit rotation to the shaft from a motor. An electronic speed control unit is used to vary the speed of the motor as required. A 6 mm diameter cylindrical pin whose contacting foot is flat, made of mild steel, fitted on a holder is subsequently fitted with an arm. The arm is pivoted with a separate base in such a way that the arm with the pin holder can rotate vertically and horizontally about the pivot point with very low friction. Sliding speed can be varied by two ways (i) by changing the frictional radius and (ii) by changing the rotational speed of the shaft. In this research, sliding speed is varied by changing the rotational speed of the shaft while maintaining 25 mm constant frictional radius. To measure the frictional force acting on the pin during sliding on the rotating plate, a load cell (TML, Tokyo Sokki Kenkyujo Co. Ltd, CLS-10NA) along with its digital indicator (TML, Tokyo Sokki Kenkyujo Co. Ltd, Model no. TD-93A) was used. The coefficient of friction was obtained by dividing the frictional force by the applied normal force (load). Wear was measured by weighing the test sample with an electronic balance before and after the test and then the difference in mass was converted to wear rate. To measure the surface roughness of the test samples, Taylor Hobson Precision Roughness Checker (Surtronic 25) was used. Each test was conducted for 30 minutes of rubbing time with new pin and test sample. Furthermore, to ensure the reliability of the test results, each test was repeated five times and the scatter in results was small, therefore the average values of these test results were taken into consideration. The detail experimental conditions are shown in Table 1.

RESULTS AND DISCUSSION

Figure 2 shows the variation of friction coefficient with the duration of rubbing at different normal loads for teflon sliding against smooth mild steel conterface. During experiment, the sliding velocity and relative humidity were 1 m/s and 70% respectively. Curves 1, 2 and 3 of this figure are drawn for normal laod 10, 15 and 20 N respectively. Curve 1 of this figure shows that during the starting, the value of friction coefficient is 0.134 and then increases very steadily up to 0.176 over a duration of 20 minutes of rubbing and after that it remains constant for the rest of the experimental time.

These findings are in agreement with the findings of Chowdhury and Helali [4]. At starting of experiment, the friction force is low due to contact between superficial layer of pin and disc. Because of ploughing effect, trapped wear particles between the contacting surfaces and surface roughening of the disc, friction force increases with rubbing time. After the running-in process for a certain duration, surface roughness and other parameters reached to a steady state value and for this reason, there is no change in friction with time. Curves 2 and 3 show that for the high normal load, the friction coefficient is less and the trend in variation of friction coefficient is almost the same as for curve 1. From these curves, it is also observed that time to reach steady state values is different for different normal load. From the obtained results it is found that at normal load 10, 15 and 20 N, telon takes 20, 17 and 15 minutes respectively to reach steady friction. It indicates that the higher the normal load, time to reach constant friction is less. This may be due to the fact that the higher the normal load, the surface roughness and other parameters take less time to stabilize.

Figure 3 shows the effect of the duration of rubbing on the value of friction coefficient at different normal loads for teflon sliding against rough mild steel counter face at sliding velocity 1 m/s and relative humidity 70%. Curve 1 of this figure drawn for normal load 10 N, shows that during starting of the experiment, the value of friction coefficient is 0.154 which rises for 22 minutes to a value of 0.188 and then it becomes steady for the rest of the experimental time. Almost similar trends of variation are observed in curves 2 and 3 which are drawn for load 15 and 20 N respectively. From these curves, it is found that time to reach steady friction is different for different normal loads. At normal load 10, 15 and 20 N, teflon-mild steel rough pair takes 22, 19 and 16 minutes respectively to reach steady friction That is, higher the normal load, tefon-mild steel rough pair takes less time to stabilize.

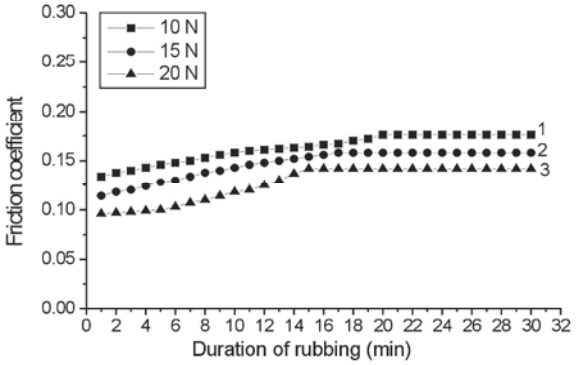

Fig. 2: Friction coefficient as a function of duration of rubbing at different normal loads (sliding velocity: 1 m/s, relative humidity: 70%, test sample: teflon, pin: mild steel, smooth)

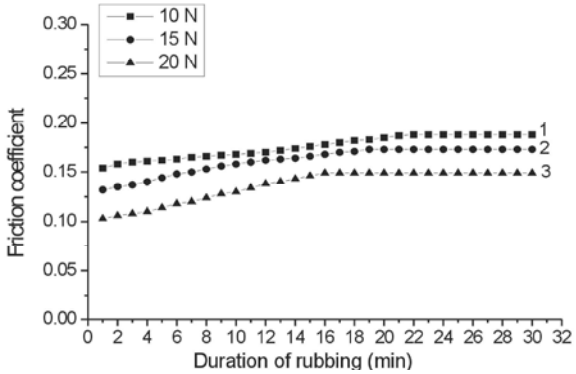

Fig. 3: Friction coefficient as a function of duration of rubbing at different normal loads (sliding velocity: 1 m/s, relative humidity: 70%, test sample: teflon, pin: mild steel, smooth)

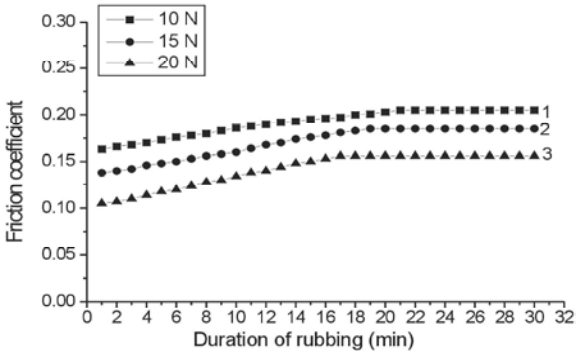

Fig. 4: Friction coefficient as a function of duration of rubbing at different normal loads (sliding velocity: 1 m/s, relative humidity: 70%, test sample: teflon, pin: mild steel, smooth)

Figure 4 shows the effect of the duration of rubbing on the value of friction coefficient at different normal load for nylon sliding against smooth mild steel counterface. Curve 1 of this figure drawn for normal load 10 N, shows

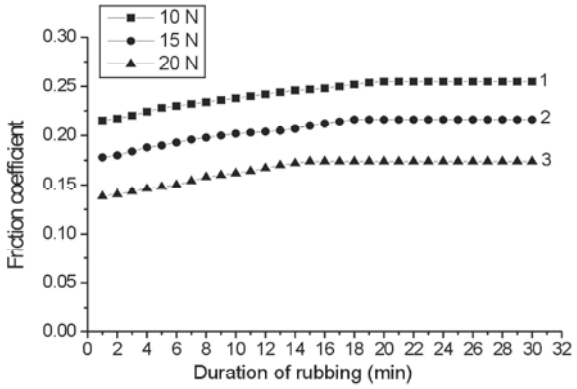

Fig. 5: Friction coefficient as a function of duration of rubbing at different normal loads (sliding velocity: 1 m/s, relative humidity: 70%, test sample: nylon, pin: mild steel, rough)

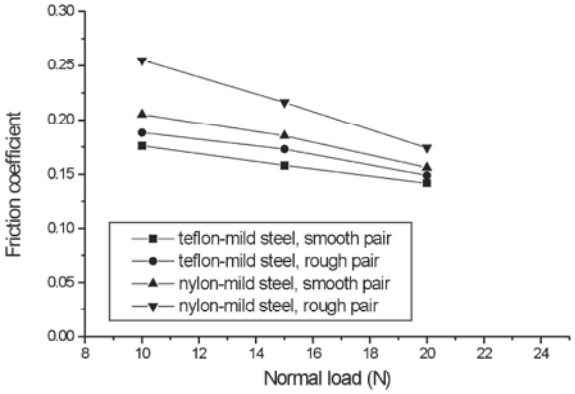

Fig. 6: Friction coefficient as a function of Normal load for teflon and nylon for different counterface surface conditions (Sliding velocity: 1 m/s, relative humidity: 70%)

that during starting of the experiment, the value of friction coefficient is 0.163 which rises for 21 minutes to a value of 0.205 and then it becomes steady for the rest of the experimental time. Almost similar trends of variation are observed in curves 2 and 3 which are drawn for load 15 and 20 N, respectively. From the obtained results, it can also be seen that time to reach constant friction is different for different normal load and higher the normal load, nylon takes less time to stabilize.

Several experiments are conducted to observe the effect of duration of rubbing on friction coefficient at different sliding speeds for nylon sliding against rough mild steel counter face and these results are presented in Figure 5.

Curve 1 of this figure drawn for normal load 10 N, shows that during starting of the experiment, the value of friction coefficient is 0.215 which rises for 20 minutes to a value of 0.255 and then it becomes steady for the rest of the experimental time. Almost similar trends of variation are observed in curves 2 and 3 which are drawn for load 15 and 20 N respectively. From these curves, it is found that time to reach steady friction is different for different normal loads. At normal load 10, 15 and 20 N, nylon-mild steel rough pair takes 20, 18 and 15 minutes respectively to reach steady friction That is, higher the normal load, glass fiber-mild steel rough pair takes less time to stabilize.

Figure 6 shows comparison of the variation of friction coefficient with normal load for teflon-mild steel smooth, teflon-mild steel rough, nylon-mild steel smooth and nylon-mild steel rough sliding pairs. Curves of this figure are drawn from steady values of friction coefficient shown in Figures 2-5 for teflon-mild steel smooth, teflon-mild steel rough, nylon-mild steel smooth and nylon-mild steel rough sliding pairs, respectively (to ensure the reliability of test results, each test was repeated five times and curves 1-3 of Figures 2-5 represent average value of five experiments). It is shown that the friction coefficient varies from 0.176 to 0.142, 0.188 to 0.149, 0.205 to 0.156 and 0.255 to 0.174 with the variation of normal load from 10 to 20 N for for teflon-mild steel smooth, teflon-mild steel rough, nylon-mild steel smooth and nylon-mild steel rough sliding pairs, respectively. From the obtained results, it can be seen that the coefficient of friction decreases with the increase in applied load. It is known that tribological behavior of polymers can be associated with their viscoelastic and temperature-related properties. Sliding contact of two materials results in heat generation at the asperities and hence increases in temperature at the frictional surfaces of the two materials which influences the viscoelastic property in the response of materials stress, adhesion and transferring behaviors [27]. From the obtained results, it can also be seen that the highest values of the friction coefficient are obtained for nylon-mild steel rough pair and the lowest values of friction coefficient are obtained for teflon-mild steel smooth pair. The values of friction coefficient of teflon-mild steel rough pair and nylon-mild steel smooth pair are found in between the highest and lowest values. It is noted that the friction coefficients of nylon-mild steel smooth pair pair are higher than that of teflon-mild steel rough pair. From this figure, it is also found that at identical conditions, the values of friction coefficient of teflon and nylon sliding against smooth mild steel counterface is lower than that of teflon and nylon sliding against rough mild steel counterface. It was found that after friction tests, the average roughness of teflon-mild steel smooth pair, teflon-mild steel rough pair, nylon-mild

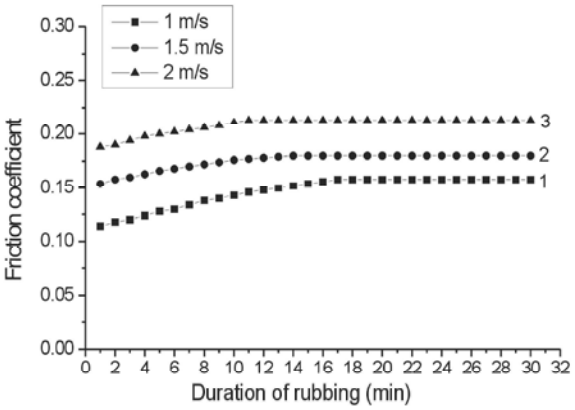

Fig. 7: Friction coefficient as a function of duration of rubbing at different sliding velocities (normal load: 15 N, relative humidity: 70%, test sample: teflon, pin: mild steel, smooth)

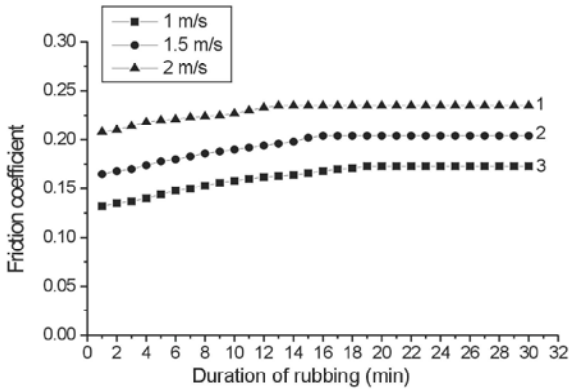

Fig. 8: Friction coefficient as a function of duration of rubbing at different sliding velocities (normal load: 15 N, relative humidity: 70%, test sample: teflon, pin: mild steel, smooth)

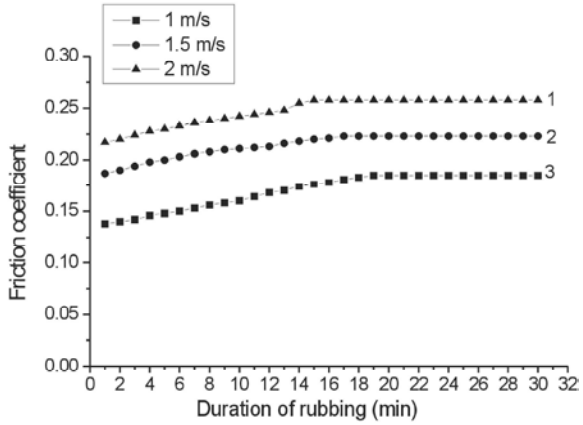

Fig. 9: Friction coefficient as a function of duration of rubbing at different sliding velocities (normal load: 15 N, relative humidity: 70%, test sample: nylon, pin: mild steel, smooth)

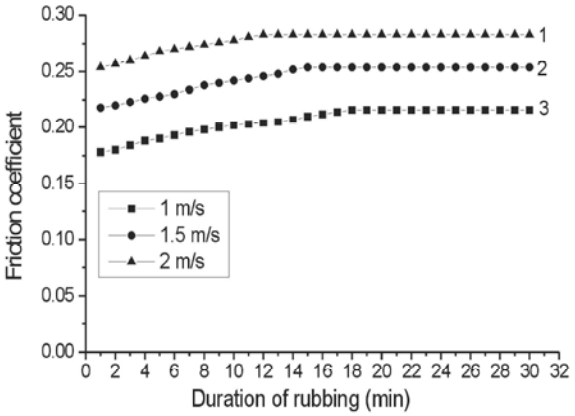

Fig. 10: Friction coefficient as a function of duration of rubbing at different sliding velocities (normal load: 15 N, relative humidity: 70%, test sample: nylon, pin: mild steel, smooth)

steel rough pair and nylon-mild steel smooth pair pair varied from 0.85-1.25, 1.15-1.55 and 1.45-1.56 and 1.57-1.81 ìm respectively.

Figures 7, 8, 9 and 10 show the variation of friction coefficient with the duration of rubbing at different sliding velocities for teflon-mild steel smooth, teflon-mild steel rough, nylon-mild steel smooth and nylon-mild steel rough sliding pairs, respectively at normal load 15 N and relative humidity 70%. Curves 1, 2 and 3 of Fig. 7 are drawn for sliding velocity 1, 1.5 and 2 m/s respectively.

Curve 1 of this figure shows that at initial stage of rubbing, the value of friction coefficient is 0.114 which increases almost linearly up to 0.158 over a duration of 17 minutes of rubbing and after that it remains constant for the rest of the experimental time. At starting of experiment, the friction force is low due to contact between superficial layer of pin and disc. Because of ploughing effect, trapped wear particles between the contacting surfaces and surface roughening of the disc, friction force increases with rubbing time. After the running-in process for a certain duration, surface roughness and other parameters reached to a steady state value and for this reason, there is no change in friction with time. Curves 2 and 3 show that for the higher sliding velocity, the friction coefficient is more and the trend in variation of friction coefficient is almost the same as for curve 1. From these curves, it is also observed that time to reach steady state value is different for different sliding velocity. From the results it is found that gear fiber-mild steel smooth pair at sliding velocity 1, 1.5 and 2 m/s takes to reach constant friction 17, 14 and 11 minutes respectively. It indicates that the higher the sliding velocity, time to reach constant

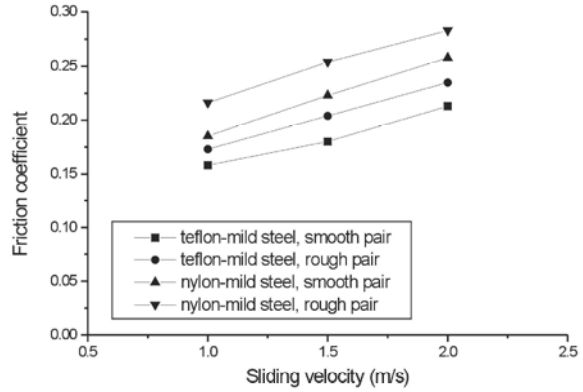

Fig. 11: Friction coefficient as a function of Normal load for telon and nylon for different counterface surface conditions (normal load: 15 N, relative humidity: 70%)

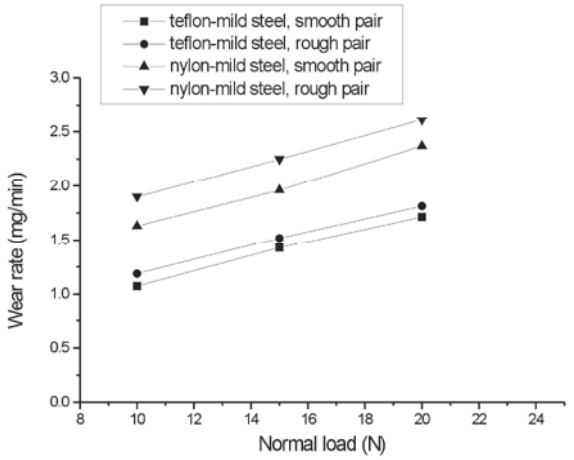

Fig. 12: Wear rate as a funtion of Normal load for teflon and nylon for different counterface surface conditions (Sliding Velocity: 1 m/s, relative humidity: 70%)

friction is less. This may be due to the higher the sliding velocity, the surface roughness and other parameters take less time to stabilize. From Figs. 8, 9 and 10, it can be observed that the trends in variation of friction coefficient with the duration of rubbing are very similar to that of Fig. 7 but the values of friction coefficient are different for telon-mild steel rough pair, nylon-mild steel smooth pair and. nylon-mild steel rough pair.

Figure 11 shows the comparison of the variation of friction coefficient with sliding speed for teflon-mild steel smooth, teflon-mild steel rough, nylon-mild steel smooth and nylon-mild steel rough sliding pairs. Curves of this figure are drawn from steady values of friction coefficient shown in Figures 7–10 for teflon-mild steel smooth, teflon-mild steel rough, nylon-mild steel smooth and nylon-mild steel rough sliding pairs. It is shown that the friction coefficient varies from 0.158 to 0.213, 0.173 to 0.235, 0.185 to 0.258 and 0.216 to 0.283 with the variation of sliding speed from 1 to 2 m/s for teflon-mild steel smooth, teflon-mild steel rough, nylon-mild steel smooth and nylon-mild steel rough sliding pairs respectively. From these results it is seen that the values of friction coefficient increase almost linearly with sliding speed. These findings are in agreement with the findings of Mimaroglu *et al*. and Unal *et al*. [27,28]. With the increase in sliding speed, the frictional heat may decrease the strength of the materials and high temperature results in stronger or increased adhesion with pin [27,51]. The increase of friction coefficient with sliding speed can be explained by the more adhesion of counterface pin material on disc. From the obtained results, it can also be seen that the highest values of the friction coefficient are obtained for nylon-mild steel rough pair and the lowest values of friction coefficient are obtained for teflon-mild steel smooth pair. The values of friction coefficient of teflon-mild steel rough pair and nylon-mild steel smooth pair are found in between the highest and lowest values. It is noted that the friction coefficients of nylon-mild steel smooth pair pair are higher than that of teflon-mild steel rough pair. From this figure, it is also found that at identical conditions, the values of friction coefficient of teflon and nylon sliding against smooth mild steel counterface is lower than that of teflon and nylon sliding against rough mild steel counterface. It was found that after friction tests, the average roughness of teflon-mild steel smooth pair, teflon-mild steel rough pair, nylon-mild steel rough pair and nylon-mild steel smooth pair pair varied from .95-1.35, 1.25-1.68 and 1.57-1.78 and 1.66-1.88 ìm respectively.

Variations of wear rate with normal load for gear fiber and glass fiber sliding against smooth or rough mild steel counterfaces are shown in Fig. 12. The experimental results indicate that the curves drawn showing the variation of wear rate from 1.075 to 1.713, 1.189 to 1.813, 1.63 to 2.37 and 1.898 to 2.61 mg/min with the variation of normal load from 10 to 20 N for for teflon-mild steel smooth, teflon-mild steel rough, nylon-mild steel smooth and nylon-mild steel rough sliding pairs respectively. From these curves, it is observed that wear rate increases with the increase of normal load for all types of sliding pairs. When the load on the pin is increased, the actual area of contact would increase towards the nominal contact area, resulting in increased frictional force between two sliding surfaces. The increased frictional force and real surface area in contact causes higher wear.

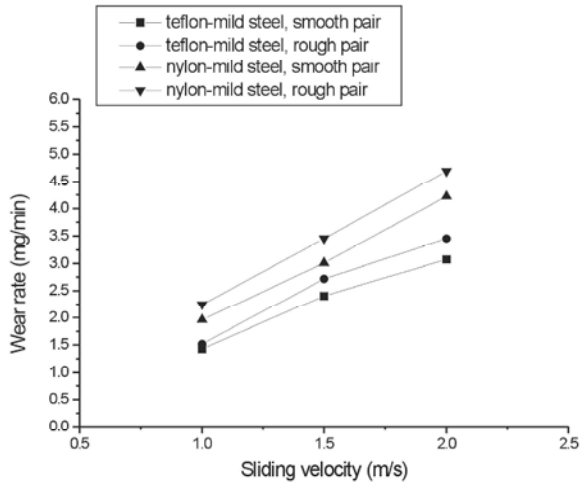

Fig. 13: Wear rate as a funtion of Normal load for teflon and nylon for different counterface surface conditions (normal load: 15 N, relative humidity: 70%)

This means that the shear force and frictional thrust are increased with increase of applied load and these increased in values accelerate the wear rate. Similar trends of variation are also observed for mild steel–mild steel couples [52], i.e wear rate increases with the increase in normal load. Figure 12 also shows the comparison of the variation of wear rate with normal load for teflon and nylon under different pin surface conditions. From the obtained results, it can also be seen that the highest values of the wear rate are obtained for nylon-mild steel rough pair and the lowest values of wear rate are obtained for teflon-mild steel smooth pair. The values of wear rate of teflon-mild steel rough pair and nylon-mild steel smooth pair are found in between the highest and lowest values. It is noted that the wear rates of nylon-mild steel smooth pair are higher than that of teflon-mild steel rough pair. From this figure, it is also found that at identical conditions, the values of wear rate of teflon and nylon sliding against smooth mild steel counterface is lower than that of teflon and nylon sliding against rough mild steel counterface.

Variations of wear rate with sliding velocity for Teflon and nylon mating with smooth or rough mild steel counterfaces are presented in Fig. 13. Curves show the variation of wear rate from 1.427 to 3.075, 1.518 to 3.45, 1.96 to 4.22 and 2.247 to 4.69 mg/min with the variation in sliding speed from 1 to 2 m/s for teflon-mild steel smooth, teflon-mild steel rough, nylon-mild steel smooth and nylon-mild steel rough sliding pairs respectively. From these curves, it is observed that wear rate increases with the increase in sliding speed for all types of material combinations. These findings are in agreement with the findings of Mimaroglu *et al* and Suresha *et al*. [27, 38]. This is due to the fact that duration of rubbing is same for all sliding velocities, while the length of rubbing is more for higher sliding velocity. The reduction of shear strength of the material and increased true area of contact between contacting surfaces may have some role on the higher wear rate at higher sliding velocity [51]. Figure 13 also shows the comparison of the variation of wear rate with sliding velocity for different sliding pairs. From the obtained results, it can also be seen that the highest values of the wear rate are obtained for nylon-mild steel rough pair and the lowest values of wear rate are obtained for teflon-mild steel smooth pair. The values of wear rate of teflon-mild steel rough pair and nylon-mild steel smooth pair are found in between the highest and lowest values. It is noted that the wear rates of nylon-mild steel smooth pair are higher than that of teflon-mild steel rough pair. From this figure, it is also found that at identical conditions, the values of wear rate of teflon and nylon sliding against smooth mild steel counterface is lower than that of teflon and nylon sliding against rough mild steel counterface. It is due to the fact that rough surfaces generally wear more quickly and have higher friction coefficients than smooth surfaces.

CONCLUSION

The presence of normal load and sliding velocity indeed affects the friction force considerably. Within the observed range, the values of friction coefficient decrease with the increase in normal load while friction coefficients increase with the increase in sliding velocity for gear fiber and glass fiber sliding against smooth or rough mild steel pin. Friction coefficient varies with the duration of rubbing and after certain duration of rubbing, friction coefficient becomes steady for the observed range of normal load and sliding velocity. Wear rates of gear fiber and glass mating with smooth or rough mild steel counterface increase with the increase in normal load and sliding velocity. The highest values of the friction coefficient and wear rate are obtained for nylon-mild steel rough pair and the lowest values of friction coefficient and wear rate are obtained for teflon-mild steel smooth pair. The values of friction coefficient and wear rate of teflon-mild steel rough pair and nylon-mild steel smooth pair are found in between the highest and lowest values. Friction coefficients and wear rates of nylon-mild steel smooth pair pair are higher than that of teflon-mild steel rough pair. At identical conditions, the values of friction

coefficient of teflon and nylon sliding against smooth mild steel counterface is lower than that of teflon and nylon sliding against rough mild steel counterface.

As (i) the friction coefficient decreases with the increase in normal load (ii) the values of friction coefficient increase with the increase in sliding velocity (iii) wear rate increases with the increase in normal load and sliding velocity and (iv) the magnitudes of friction coefficient and wear rate are different for smooth and rough counterface pins and type of materials, therefore maintaining an appropriate level of normal load, sliding velocity as well as appropriate choice of counterface surface condition and tested materials, friction and wear may be kept to some lower value to improve mechanical processes.

REFERENCE

1. Archard, J.F., 1980. Wear theory and mechanisms, Wear Control Handbook, ASME, New York, NY.
2. Tabor, D., 1987. Friction and wear – developments over the last 50 years, keynote address, Proceedings of the International Conference of Tribology – Friction, Lubrication and Wear, Queen Elizabeth II Conference Centre, London,Institute of Mechanical Engineering, London, pp: 157-72.
3. Kukureka, S.N., Y.K. Chen, C.J. Hooke and P. Liao, 1995. The wear mechanisms of acetal in unlubricatedrolling-sliding contact, Wear, 185: 1-8.
4. Chowdhury, M.A. and M.M. Helali, 2008. The effect of amplitude of vibration on the coefficient of friction fordifferent materials, Tribology International, 41(4): 307-14.
5. Chowdhury, M.A. and M.M. Helali, 2009a. The frictional behavior of composite materials under horizontal vibration, Industrial Lubrication and Tribology, 61(5): 246-53.
6. Chowdhury, M.A. and M.M. Helali, 2009b. The frictional behavior of materials under vertical vibration, Industrial Lubrication and Tribology, 61(3): 154-60.
7. El-Tayeb, N.S.M. and I.M. Mostafa, 1996. The effect of laminate orientations on friction and wear mechanisms of glass reinforced polyester composite, Wear, 195: 186-91.
8. El-Tayeb, N.S.M. and R.M. Gadelrab, 1996. Friction and wear properties of e-glass fiber reinforced epoxy compositesunder different sliding contact conditions, Wear, 192: 112-17.
9. Bahadur, S. and Y. Zheng, 1990. Mechanical and tribological behavior of polyester reinforced with short glass fibers, Wear, 137: 251-66.
10. Bahadur, S. and V.K. Polineni, 1996. Tribological studies of glass fabric-reinforced polyamide composites filled with CuO and PTFE, Wear, 200: 95-104.
11. Watanabe, M., 1968. The friction and wear properties of nylon, Wear, 110: 379-88.
12. Tanaka, K., 1982. Transfer of semi crystalline polymers sliding against smooth steel surface, Wear, 75: 183-99.
13. Bahadur, S. and D. Tabor, 1985. Role of fillers in the friction and wear behavior of high-density polyethylene, in Lee, L.H. (Ed.), Polymer Wear and Its Control, ACS Symposium Series, ACS Publications, Washington, DC, 287: 253-68.
14. Pihtili, H. and N. Tosun, 2002a. Effect of load and speed on the wear behavior of woven glass fabrics and aramid fiber-reinforced composites, Wear, 252: 979-84.
15. Pihtili, H. and N. Tosun, 2002b. Investigation of the wear behavior of a glass fiber-reinforced composite and plain polyester resin, Composites Science and Technology, 62: 367-70.
16. Bijwe, J., U.S. Tewari and P. Vasudevan,1990. Friction and wear studies of polyetherimide composites, Wear, 138: 61-76.
17. Bijwe, J., J. Indumathi, J. John Rajesh and M. Fahim, 2001. Friction and wear behavior of polyetherimide composites in various wear modes, Wear, 249: 715-26.
18. Bijwe, J. and J. Indumathi, 2004. Influence of fibers and solid lubricants on low amplitude oscillating wear of polyetherimide composites, Wear, 257(5/6): 562-72.
19. Bijwe, J., J. Indumathi and A.K. Ghosh, 2004. Role of fabric reinforcement on the low amplitude oscillating wear of polyetherimide composites, Wear, 256(1/2): 27-37.
20. Zhang, S.W., 1998. State-of-the-art of polymer tribology', Tribol. Int., 31(1-3): 49-60.
21. Kowandy, C., C. Richard and Y.M. Chen, 2008. Characterization of wear particles for comprehension of wear mechanisms case of PTFE against cast iron, Wear, 265(11–12): 1714–1719.
22. Yamaguchi, Y., 1990. Tribology of Plastic Materials: Their Characteristics and Applications to Sliding Components, Elsevier, Amsterdam.
23. Hooke, C.J., S.N. Kukureka, P. Liao, M. Rao and Y.K. Chen, 1996. The friction and wear of polymers innon-conformal contacts, Wear, 200: 83-94.
24. Lawrence, C.C. and T.A. Stolarski, 1989. Rolling contact wear of polymers: a preliminary study, Wear, 132: 83-91.

25. Feyzullahoglu, E. and Z. Saffak, 2008. The tribological behavior of different engineering plastics under dry friction conditions', Mater. Design, 29(1): 205-211.
26. Wang, Y.Q. and J. Li, 1999. Sliding wear behavior and mechanism of ultra-high molecular weight polyethylene', Mater. Sci. Eng., 266(1-2): 155-160.
27. Mimaroglu, A., H. Unal and T. Arda, 2007. Friction and wear performance of pure and glass fiber reinforced poly-ether-imide on polymer and steel counter face materials, Wear, 262(11-12): 1407-1413.
28. Unal, H., U. Sen and A. Mimaroglu, 2004. Dry sliding wear characteristics of some industrial polymers against steel counterface', Tribol. Int., 37(9): 727-732.
29. Unal, H., U. Sen and A. Mimaroglu, 2006. An approach to friction and wear properties ofpolytetrafluoroethylene composite, Mater. Design, 27(8): 694-699.
30. Sirong, Y., Yu. Zhongzhen and Y.W. Mai, 2007. Effects of SEBS-g-MA on tribological behavior of nylon 66/organoclay nanocomposites, Tribol. Int., 40(5): 855-862.
31. Bahadur, S. and A. Kapoor, 1992. The effect of ZnF2, ZnS and PbS fillers on the tri bological behavior of nylon 11, Wear, 155(1): 49-61.
32. Wang, J., M. Gu, S. Bai and S. Ge, 2003. Investigation of the influence of MoS2 filler on the tribological properties of carbon fiber reinforced nylon 1010 composites, Wear, 255(1-6): 774-779.
33. Tsukizoe, T. and N. Ohmae, 1983. Friction and wear of advanced composite materials, FibreSci. Technol., 18(4): 265-286.
34. Franklin, S.E., 2001. Wear experiments with selected engineering polymers and polymer composites under dry reciprocating sliding conditions, Wear, 251(1-12): 1591-1598.
35. Nuruzzaman, D.M., M.A. Chowdhury and M.L. Rahaman, 2011. Effect of duration of rubbing and normal load on friction coefficient for polymer and composite materials', Ind. Lubr. Tribol., 63(5): 320-326.
36. Benabdallah, H., 2003. 'Friction and wear of blended polyoxymethylene sliding against coated steel plates, Wear, 254(12): 1239-1246.
37. Unal, H., A. Mimaroglu, U. Kadioglu and H. Ekiz, 2004. Sliding friction and wear behavior of polytetrafluoroethylene and its composites under dry conditions, Mater. Design, 25(3): 239-245.
38. Suresha, B., G. Chandramohan, P. Samapthkumaran, S. Seetharamu and S. Vynatheya, 2006. Friction and wear characteristics of carbon-epoxy and glass-epoxy woven roving fiber composites, J. Reinf. Plast. Comp., 25(7): 771-782.
39. Cho, M.H., S. Bahadur and A.K. Pogosian, 2005. Friction and wear studies using Taguchi method on polyphenylene sulfide filled with a complex mixture of MoS2, Al2O3 and other compounds, Wear, 258(11-12): 1825-1835.
40. Santner, E. and H. Czichos, 1989. Tribology of polymers, Tribology International, 22(2): 103-9.
41. Tevruz, T., 1998. Tribological behaviours of carbon-filled polytetrafluoroethylene dry journal bearings, Wear, 221: 61-8.
42. Tevruz, T., 1999. Tribological behaviours of bronze-filled polytetrafluoroethylene dry journal bearings, Wear, 230: 61-9.
43. Anderson, J.C., 1986. The wear and friction of commercialpolymers and composites, in Friedrich, K. (Ed.), Frictionand Wear and Polymer Composites, Composite MaterialsSeries, Elsevier, Amsterdam, 1: 329-62.
44. Stuart, B.H., 1998. Tribological studies of poly(ether ether ketone) blends", Tribology International, 31(11): 647-51.
45. Unal, H. and A. Mimaroglu, 2003. Friction and wear behavior of unfilled engineering thermoplastics, Material Design, 24: 183-7.
46. Unal, H. and A. Mimaroglu, 2003. Influence of test conditions on the tribological properties of polymers, Industrial Lubrication and Tribology, 55(4): 178-83.
47. Suresha, B., G. Chandramohan, J.N. Prakash, V. Balusamy and K. Sankaranarayanasamy, 2006a. The role of fillerson friction and slide wear characteristics in glass-epoxy composite systems, Journal of Minerals & Materials Characterization & Engineering, 5(1): 87-101.
48. El-Tayeb, N.S.M., B.F. Yousif and T.C. Yap, 2006. Tribological studies of polyester reinforced with CSM450-R-glass fiber sliding against smooth stainless steel counterface, Wear, 261: 443-52.
49. Clerico, M. and V. Patierno, 1979. Sliding wear of polymeric composites, Wear, 53(2): 279-97, 299-301.
50. Yang, E.L., 1992. Effect of crystalline and amorphous phases on the transfer of polytetrafluoroethylene (PTFE)onto metallic substrates, Journal of Materials Research, 7(11): 3139-49.
51. Bhushan, B., 1999. Principle and Applications of Tri bology, John Wiley & Sons, Inc., New York.
52. Chowdhury, M.A. and M.M. Helali, 2007. The Effect of Frequency of Vibration and Humidity on the Wear rate, Wear, 262: 198-203.