

## Photocatalytic Degradation of Kermanshah Refinery Wastewater Using Nano-TiO<sub>2</sub> Supported on Bentonite

*<sup>1</sup>Daraei Ali and <sup>2,3</sup>Ghasemi Mobtaker Hosein*

<sup>1</sup>Department of Chemistry, Kermanshah Branch of ACECR, Kermanshah, Iran

<sup>2</sup>Faculty of Chemistry, Tehran North Branch, Islamic Azad University, Tehran, Iran

<sup>3</sup>NSTRI, Jaber Ibn Hayan Research Laboratory, Tehran, Iran

---

**Abstract:** TiO<sub>2</sub>/bentonite nanocomposite were prepared by sol gel method. XRD, BET, EDX and SEM were used to characterize the prepared photocatalyst. The methods confirmed the deposition of TiO<sub>2</sub> on bentonite. Loading the TiO<sub>2</sub> increased the surface area of the composite comparing to pure TiO<sub>2</sub> and bentonite. The photocatalytic properties of nanocomposite was tested in degradation of a waste from a refinery plant and it was compared with pure titania and bentonite with and without UV irradiation. Titania loaded nanocomposite has the greatest activity comparing the others. Increasing the catalyst weight and temperature led to increasing the photocatalytic degradation percent. GC analysis of the sample in optimum condition showed that the prepared photocatalyst can degrade efficiently all of the organic pollutants were present in the waste, in 4 h.

**Key words:** Photocatalyst • Nano-TiO<sub>2</sub> • Sol-Gel, Bentonite

---

### INTRODUCTION

Organic pollution arising from various industries is a challenging issue nowadays and finding an efficient way to treat these types of wastes has a great importance. Advanced oxidation processes (AOPs) have been used in past decades as a promising technology for degradation of such a pollutant. Mineralization of the organics in this technology proceeds by highly reactive hydroxyl radical attack and since it has no selectivity, the method can be used for wide range of organic contaminants. Among the semiconductor, TiO<sub>2</sub>, because of its high photocatalytic activity, stability, low price and non-toxicity is far superior candidate [1-5].

A large number of researches have been done to investigate the photocatalytic activity of TiO<sub>2</sub> considering its structure and size [6-11]. Most of studies have been done on anatase and rutile phases of nanostructured TiO<sub>2</sub>, while scarce reports are demonstrated on brookite [12].

The photocatalyst can be used as suspension in wastewater or immobilized on inert surfaces. Using the photocatalyst as suspension needs a recovery step after

the reaction, but coating the catalyst on a porous material can avoid the step, resulting in saving the energy and cost. Moreover TiO<sub>2</sub> particles aggregate in suspension, resulting in small surface area, lower catalytic activity and complicating the filtration of suspensions, which makes the photocatalytic process impractical [13].

Several immobilization methods such as spray coating, sputtering, dip coating, electrophoretic deposition and sol-gel related have been proposed and various support such as activated carbon, quartz, glass beads, stainless steel, silica, aluminum and etc. have been studied [14].

In this study we investigated the degradation of Kermanshah Refinery wastes using bentonite supported TiO<sub>2</sub> as catalyst. The most significant pollutants in this wastes are aromatics, however other pollutants are present in the wastes. Conventional biological treatment methods are ineffective for degradation of these pollutants and unfortunately, there are no universally useful methods available for treatment of these wastes. In recent years, AOPs have been considered as a promising method for degradation of these wastes as demonstrated [15].

## MATERIALS AND METHODS

**Materials:** The experimental involved following steps: preparation of bentonite, synthesis of TiO<sub>2</sub>/bentonite and photo-degradation of the Kermanshah Refinery waste to investigate the photocatalytic properties of the prepared catalyst.

To activate the bentonite, it was rinsed with distilled water. As it was expected the bentonite absorbed the water and swelled, so the impurities settled down faster than it. Then the slurry was centrifuged and the bentonite was separated. It was dried at 104°C for 12 hours in an oven. HCl solution (8 M, 1:5 w/v) was added to the bentonite powder and it was activated below 70°C for 3 hours, filtrated, washed with double distilled water (to remove the excess acid) and dried at 104°C for 12 hours. The obtained powder was milled, sieved with a 270-mesh sieve and mixed with a 20% NH<sub>3</sub> solution (1:4 w/v). After stirring at room temperature for 12 hours, the mixture was filtrated, washed again to remove the residual ammonia and dried at 80°C for 16 hours. After the activation process the specific surface area increased to 83 m<sup>2</sup>/g.

Sol-gel method using titanium tetraisopropoxide was used in this research to synthesize the catalyst. 25 ml of alkoxide solution was added drop by drop to 500 ml solution of double distilled water and isopropyl alcohol (v/v ratio of 9:1), with vigorous agitation. Then the pH was adjusted at 2 using nitric acid. The mixture was agitated vigorously at 70°C for 24 hours and the stable titania sol was formed.

To synthesize the TiO<sub>2</sub>/bentonite nanophotocatalyst a 4% slurry of ammonia bentonite was prepared and 500 ml of it was loaded to the reactor. It was agitated vigorously for 1 hour for maximum absorption of water by bentonite and its efficiently swelling for separation of the layers. Then 50 ml of titania sol was added and agitated at room temperature for 24 hours. It was filtrated and washed to remove the excess titania. The product was dried at 100°C for 12 hours and then was calcined at 400°C for 2 hours.

The UV lamp (UV-C, 200 W) was used to irradiate the waste with initial COD (Chemical Oxygen Demand) of 700 ppm. The waste was for gasoline production unit and its pH was between 6.5 to 7.5 and its turbidity was about 100 NTU. Reactor volume was 1 L. Digestion systems was used for the determination of the COD.

**Characterization:** The qualitative identification of nanocomposite sample phases was made by powder

X-ray diffraction (PXRD) technique. X-ray diffraction measurement was used and it was done on a STOE STADI MP X-ray diffractometer using Cu K $\alpha$  radiation ( $\lambda = 0.15406$  nm). EDX was also used for elemental analysis of the sample. The surface area was measured by BET method, using a Coulter 100 CXO nitrogen adsorption apparatus. The nitrogen adsorption-desorption isotherms of the samples were determined by N<sub>2</sub> adsorption at 77 K. The microporous area was obtained from the t-plot of N<sub>2</sub> adsorption data at higher partial pressures. SEM was used to observe the formed composite particles and the second phase precipitated on support.

Catalytic activities of samples were determined by degradation of a Kermanshah Refinery waste sample provided by a factory in Kermanshah province of Iran. Natural bentonite, commercial TiO<sub>2</sub> nanopowder and the composite were used for degradation of the waste in various pHs, catalyst weight and temperatures. The concentrations were detected using a Cary UV-Vis spectrometer.

## RESULT AND DISCUSSION

Table 1 shows the EDX analyses of samples prepared using various volumes of titania sol to load the titania on bentonite. It can be observed that with increasing the volume of the used sol, the amount of the loaded titania is increased from about 11 up to 24%. Figure 1 shows that the loading percent of titania is about to be saturated in 24%. Excess amount of titania is removed by washing.

Figure 2 shows the XRD pattern of pure anatase and titania loaded bentonite. It can be seen that anatase peaks at 25.48°, 38.24°, 48.12°, 54.96° and 63.48° are present in titania loaded bentonite. XRD pattern shows that the TiO<sub>2</sub> deposited on the surface of bentonite has not the crystallinity of the pure one.

Figure 3 shows the SEM of TiO<sub>2</sub>/bentonite photocatalyst. It can be seen that the particles are formed in various sizes. TiO<sub>2</sub> particles can be observed on the surface of bentonite. The particles have not ordered forms.

By coating the TiO<sub>2</sub> on bentonite the surface area of the nanocomposite was increased and reaches to 219 m<sup>2</sup>/g. Other parameters are presented in Table 2 and Figure 4. The surface area of commercial nano-TiO<sub>2</sub> was 152 m<sup>2</sup>/gr. Increasing the surface area leads to increase the exposed surface of photocatalyst and consequently increasing the activity of photocatalyst, which results in faster degradation of pollutants.

Table 1: EDX Analysis of nanocomposite prepared using various volume of titania sol

Element	15		20		25		30		35	
	W t%	At %								
Mg k	1.35	1.79	1.01	1.15	0.93	1.02	0.83	0.91	0.80	0.97
Al k	10.70	12.81	9.18	10.70	7.84	8.41	7.10	7.33	6.89	6.95
Si k	57.89	65.20	55.25	63.15	54.12	62.30	52.91	61.06	52.30	60.54
K k	1.39	1.06	1.30	1.03	1.18	0.94	1.03	0.84	0.61	0.57
Ca k	1.07	0.75	0.91	0.61	0.75	0.57	0.69	0.51	0.55	0.49
Ti k	14.32	11.15	18.36	15.19	21.06	18.42	23.10	20.56	24.36	21.20
Fe k	4.41	5.37	10.01	5.87	10.10	5.93	10.21	6.01	10.29	6.27
Cu k	3.87	1.87	3.98	2.03	4.02	2.41	4.13	2.73	4.20	3.01
Total	100.00	100.00	100.00	100.00	100.00	100.00	100.00	100.00	100.00	100.00

Table 2: BET analysis of the composite

Vm(cm <sup>3</sup> /gr)	Total pore volume (cm <sup>3</sup> /gr)	Mean pore diameter (nm)	BET (m <sup>2</sup> /gr)
50.183	0.3137	5.74	219

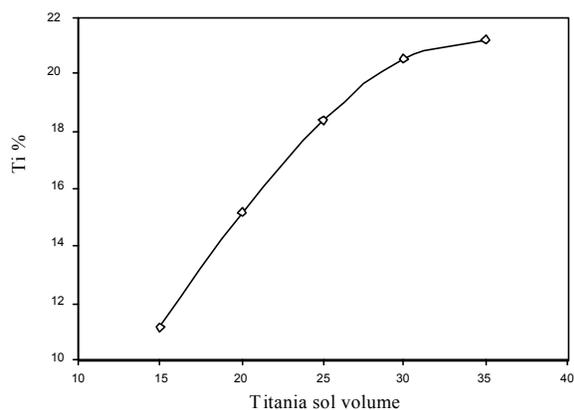


Fig. 1: Ti percent absorbed on bentonite

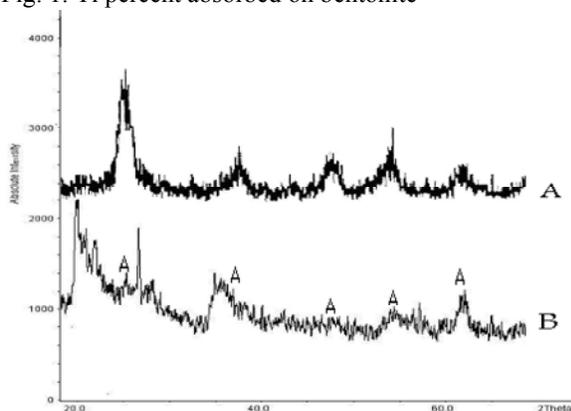


Fig. 2: XRD pattern of pure TiO<sub>2</sub> (A) and TiO<sub>2</sub> loaded bentonite (B)

To investigate the photocatalytic activity of prepared nanocomposite a waste from the refinery plant of Kermanshah with COD of 700 ppm was exposed to the nanocomposite, commercial nano-TiO<sub>2</sub> and natural bentonite with UV irradiation. The concentration was

measured using UV-Visible spectrometry. It can be observed in Figure 5 that using pure bentonite leads to concentration decrease of about 30% and the prepared nanocomposite decrease about 50% of the pollutant, but the nanocomposite degrades about 90% of the pollutants. The concentration decrease without UV irradiation can be because of adsorption. Since the nanocomposite has higher surface area rather than the pure bentonite, its adsorption property is greater. Comparing the photocatalytic activity of nanocomposite and commercial nano-TiO<sub>2</sub> revealed that the nanocomposite has greater activity than the others. It can be attributed to the smaller surface area of commercial nano-TiO<sub>2</sub>.

The effect of catalyst weight on degradation percent can be observed in Figure 6. The figure shows that increasing the catalyst weight increases the degradation percent; but the cost and separation problems should be considered for increasing the catalyst weight.

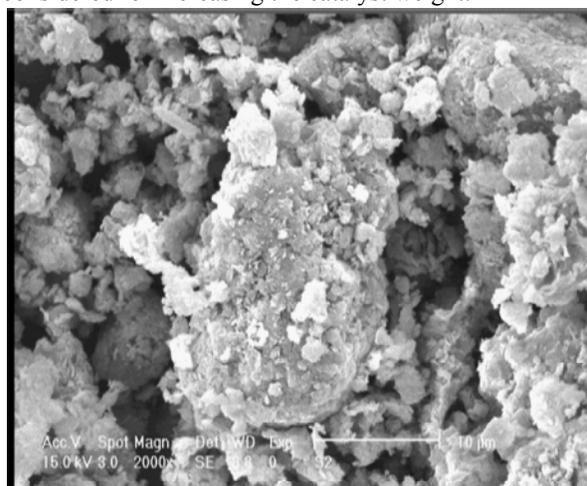


Fig. 3: SEM photograph of TiO<sub>2</sub>/bentonite

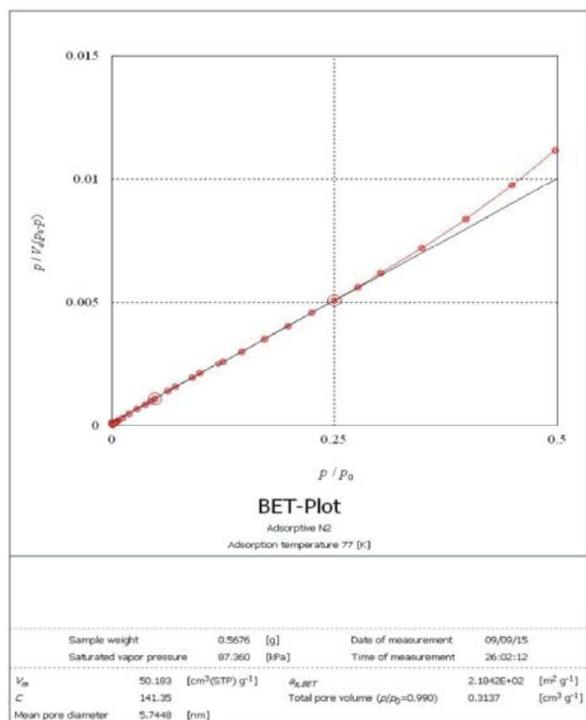


Fig. 4: N<sub>2</sub> adsorption isotherm of TiO<sub>2</sub>/bentonite nanocomposite

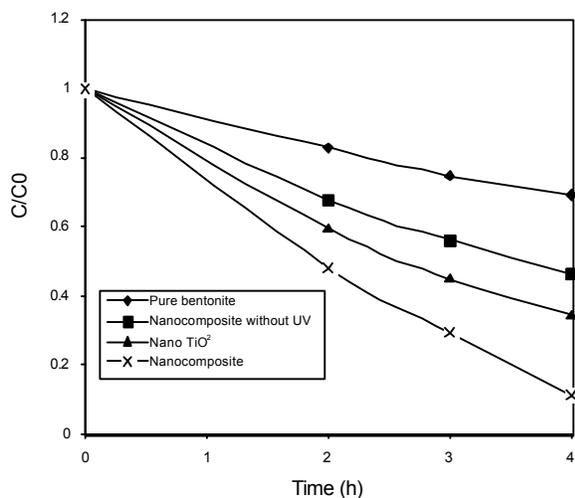


Fig. 5: Degradation ratio of the waste by UV irradiation in pH=4.5 and 1 g/L of catalyst

Temperature variation has also some effect on degradation percent. To investigate its effect three various temperatures were opt which were controlled before and during the reaction. We found out that increasing the temperature had a positive effect on degradation percent. It can be because of increasing the intensity of excitation by increasing the temperature and

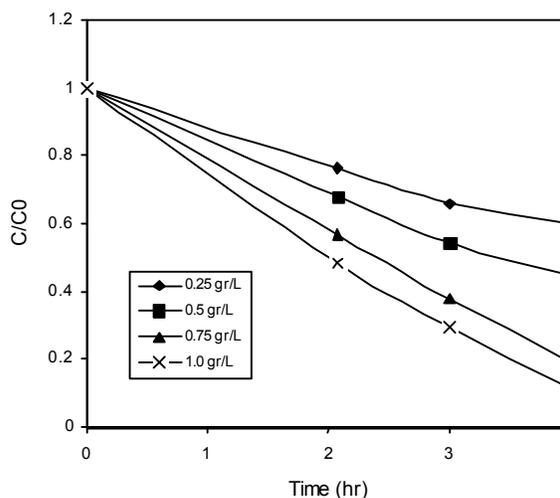


Fig. 6: Degradation ratio with various amounts of TiO<sub>2</sub>/bentonite, pH=4.5, T=25°C

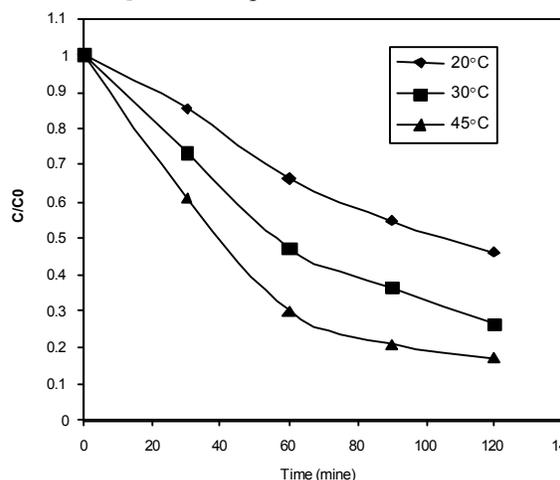


Fig. 7: The effect of temperature variation on degradation percent in pH=4.5 and 1 g/L of TiO<sub>2</sub>/bentonite

increasing the rate constant according the Arrhenius equation. Although the amount of adsorption decreases with an increase in the reaction temperature, the photocatalytic reaction competes more effectively with an electron-hole recombination and thus the photocatalytic reaction rate enhances [16]. We didn't increase the temperature to higher degrees because of considerable evaporation at high temperatures. Figure 7 shows the temperature effect on degradation percent.

The efficiency of the procedure in 4 h can be concluded from Figure 8. It shows the GC analysis of the waste obtained from Kermanshah Refinery Plant before the photocatalytic degradation in graph A and its composition after photocatalytic degradation in graph B.

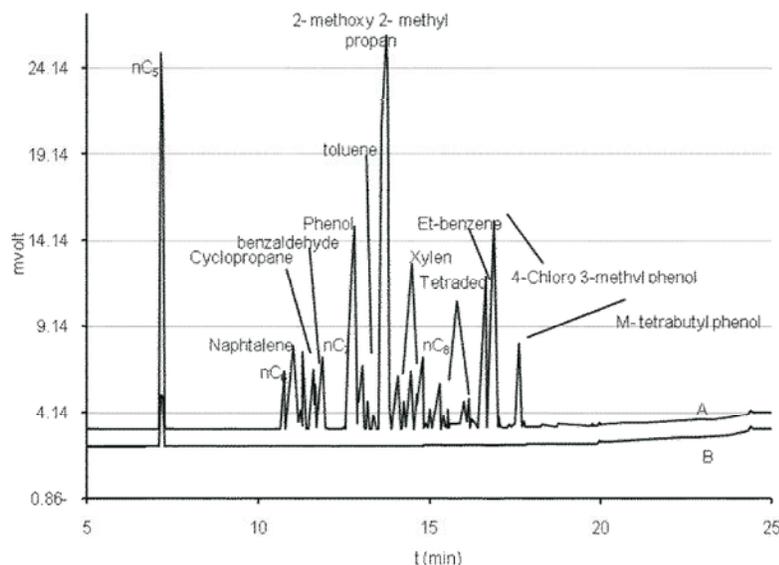


Fig. 8: Comparing the waste composition before (A) and after (B) degradation using GC analysis in pH=4.5 and 1 g/L of TiO<sub>2</sub>/bentonite

It is obvious that the photocatalytic degradation procedure has high efficiency and all of the organic compounds presented in the waste, were degraded in 4 h.

### CONCLUSION

TiO<sub>2</sub>/bentonite nanocomposite were prepared by sol gel method. It was characterized by XRD, BET, EDX and SEM. Loading the TiO<sub>2</sub> led to increase the surface area of the composite. The composite was used for photocatalytic degradation of a waste from Kermanshah Refinery Plant and the results were compared with pure titania and pure bentonit with and without irradiation of UV light. Titania loaded nanocomposite has the greatest activity Increasing the catalyst weight and temperature led to increasing the photocatalytic degradation percent. GC analysis of the sample in optimum condition showed that the prepared photocatalyst can degrade efficiently all of the organic pollutants were present in the waste, in 4 h.

### REFERENCES

- Galindo, C., P. Jacques and A. Kalt, 2001. Photooxidation of the phenylazonaphthol AO<sub>2</sub>0 on TiO<sub>2</sub>: kinetic and mechanistic investigations. *Chemosphere*, 45: 997-1005.
- Ku, Y., R.M. Leu and C.K. Lee, 1996. Decomposition of 2-chlorophenol in aqueous solution by UV irradiation with the presence of titanium dioxide. *Water Research*, 30: 2569-2578.
- Poulios, I.A., 1999. Photocatalytic Degradation of the Textile Dye Reactive Orange 16 in the Presence of TiO<sub>2</sub> Suspensions. *Environmental Science and Technology*, 20: 479-487.
- Robert, B., J.V. Dongui and J. Weber, 2003. Heterogeneous photocatalytic degradation of 3-nitroacetophenone in TiO<sub>2</sub> aqueous suspension. *Journal of Photochemical and Photobiological A: Chemistry*, 156: 195-200.
- Zielinska, B., J. Grzechulska and A.W. Morawski, 2003. Photocatalytic Decomposition of Textile Dyes on TiO<sub>2</sub> -Tytanpol A11 and TiO<sub>2</sub>-Degussa P25. *Journal of Photochemical and Photobiological A: Chemistry*, 157: 65-70.
- Liu, G., T. Wu, J. Zhao, H. Hidaka and N. Serpone, 1999. Photoassisted Degradation of Dye Pollutants. 8. Irreversible Degradation of Alizarin Red under Visible Light Radiation in Air-Equilibrated Aqueous TiO<sub>2</sub> Dispersions, *Environmental Science and Technology*, 33: 2081-2087.
- Zhao, J., T. Wu, K. Wu, K. Oikawa, H. Hidaka and N. Serpone, 1998. Photoassisted degradation of dye pollutants. 3. Degradation of the cationic dye rhodamine B in aqueous anionic surfactant/TiO<sub>2</sub> dispersions under visible light irradiation: evidence for the need of substrate adsorption on TiO<sub>2</sub> particles. *Environmental Science and Technology*, 32: 2394.

8. Hoffmann, M.R., S.T. Martin, W. Choi and D.W. Bahnemann, 1995. Environmental Applications of Semiconductor Photocatalysis. *Chemical Reviews*, 95: 69-96.
9. Konstantinou, I.K. and T.A. Albanis, 2003. Photocatalytic transformation of pesticides in aqueous titanium dioxide suspensions using artificial and solar light: intermediates and degradation pathways. *Applied Catalysis. B: Environment*, 42: 319-335.
10. Dhermendra K.T., J. Behari and P. Sen, 2008. Application of Nanoparticles in Waste Water Treatment, *World Applied Sciences Journal*, 3(3): 417-433.
11. Hosseinnia, A., M. Keyanpour-Rad and M. Pazouki, 2010, Photo-catalytic Degradation of Organic Dyes with Different Chromophores by Synthesized Nanosize TiO<sub>2</sub> Particles, *World Applied Sciences Journal*, 8(11): 1327-1332.
12. Ramesh, T., V. Saravanamuthu and M. Shik, 2008. A review on UV/TiO<sub>2</sub> photocatalytic oxidation process. *Korean Journal of Chemical Engineering*, 25(1): 64-72.
13. Torimoto, T., Y. Okawa, N. Takeda and H. Yoneyama, 1997. Effect of activated carbon content in TiO<sub>2</sub>-loaded activated carbon on photodegradation behaviors of dichloromethane. *Journal of Photochemistry and Photobiology A: Chemistry*, 103: 153-157.
14. Palominos, R.A., A. Moraa, M.A. Mondacab, M. Perez-Moya and H.D. Mansilla, 2008. Oxolinic acid photo-oxidation using immobilized TiO<sub>2</sub>. *Journal of Hazardous Materials*, 158: 460-464.
15. Muruganandham, M. and M. Swaminathan, 2006. Advanced oxidative decolourisation of Reactive Yellow 14 azo dye by UV/TiO<sub>2</sub>, UV/H<sub>2</sub>O<sub>2</sub>, UV/H<sub>2</sub>O<sub>2</sub>/Fe<sup>2+</sup> processes-a comparative study, *Separation and Purification Technology*, 48: 297-303.
16. Marandi, R., M.E. Olya, B. Vahid, M. Khosravi and M. Hatami, 0000. Kinetic Modeling of Photocatalytic Degradation of an Azo Dye Using Nano-TiO<sub>2</sub>/Polyester, *Environmental Engineering Science* (in press).